



**VICTORIA UNIVERSITY**  
MELBOURNE AUSTRALIA

*Direct Contact Membrane Distillation (DCMD):  
Experimental Study on the Commercial PTFE  
Membrane and Modelling*

This is the Accepted version of the following publication

Hwang, Ho Jung, He, Ke, Gray, Stephen, Zhang, Jianhua and Moon, Il Shik  
(2011) Direct Contact Membrane Distillation (DCMD): Experimental Study on  
the Commercial PTFE Membrane and Modelling. *Journal of Membrane  
Science*, 371 (1-2). pp. 90-98. ISSN 0376-7388

The publisher's official version can be found at  
<http://www.sciencedirect.com/science/article/pii/S0376738811000251>  
Note that access to this version may require subscription.

Downloaded from VU Research Repository <https://vuir.vu.edu.au/8997/>

1       **Direct contact membrane distillation (DCMD): experimental study on the**  
2                               **commercial PTFE membrane and modeling**

3                               Ho Jung Hwang<sup>1</sup>, Ke He<sup>1</sup>, Stephen Gray<sup>2</sup>, Jianhua Zhang<sup>2</sup>, Il Shik Moon<sup>1\*</sup>

4       <sup>1</sup>*Dept. of Chemical Engineering, Sunchon National University, 315 Maegok Dong, Suncheon*  
5                               *540-742, Chonnam, Korea*

6       <sup>2</sup>*Institute of Sustainability and Innovation, Victoria University, PO Box 14428, Melbourne,*  
7                               *Victoria 8001, Australia*

8  
9       **Abstract**

10       Membrane distillation (MD) is an alternative technology for the separation of mixtures through  
11       porous hydrophobic membranes. A commercially available PTFE (Polytetrafluoroethylene)  
12       membrane was used in Direct Contact Membrane Distillation (DCMD) to investigate the effect of  
13       module dimensions on performance. Membrane properties, such as liquid entry pressure (LEP),  
14       contact angle (CA), pore diameter, effective porosity and pore size distribution, were  
15       characterized and used in analysis. A two dimensional (2D) model containing mass, energy, and  
16       momentum balance was developed for predicting permeate flux production. Different flow  
17       modes including co-current and counter-current flow mode were studied. The effect of linear  
18       velocity on permeation flux for both wide and short, and long and narrow module designs was  
19       investigated. The mass transfer coefficients for each condition were calculated for comparison of  
20       the module designs. The effects of operating parameters such as flow mode, temperature  
21       difference, and NaCl concentration were also considered. The simulated results were validated by  
22       comparing with experimental results. Good agreement was found between the numerical  
23       simulation and the experiments.

24  
25       **Keywords:** Direct contact membrane distillation, Module geometry, Heat and mass transfer,  
26       Vapor pressure difference.

---

\* Author for Correspondence: Tel 82-61-7503581, Fax 82-61-7503581, Email-  
[ismoon@sunchon.ac.kr](mailto:ismoon@sunchon.ac.kr)

1

## 2 **1. Introduction**

3 Membrane Distillation (MD) is an emerging alternative separation technology that can be used  
4 for desalination of salty waters. By using MD, pure water can be extracted from aqueous  
5 solutions containing non-volatile contaminants through a hydrophobic, micro-porous membrane  
6 when a vapor pressure difference is established across the membrane. The hydrophobic  
7 membrane inhibits the permeation of liquid water through membrane via the high surface tension  
8 between the membrane and aqueous phase, but allows the passage of vapor. Water vapor is  
9 transported from regions of high vapor pressure to regions of lower vapor pressure [1]. In  
10 DCMD, the difference in vapor pressure is achieved via a temperature difference across the  
11 membrane, as cold liquid is passed on the permeate side of the membrane in order to condense  
12 vapor that has migrated through the membrane pores from the hot feed solution [2, 3]. Other MD  
13 configurations can be used to recover and condense the migrated vapor molecules: vacuum  
14 membrane distillation (VMD) [4], sweep gas membrane distillation (SGMD) [5] and air gap  
15 membrane distillation (AGMD) [6].

16 Since MD is a thermal process, it can operate at lower pressures than other membrane  
17 desalination processes and produces water of lower salinity [7]. Additionally, it may operate at  
18 low temperatures (40~60°C) because it has a small vapor space and high mass transfer area  
19 compared to other thermal processes [8]. Therefore, MD may be applied to treating high salinity  
20 brines where low grade heat is available, such as in industrial sites. Furthermore, treatment of  
21 high salinity wastewater, such as the concentrate from RO processes, may also be a viable  
22 application for MD.

23 The heat and mass transfer across the membrane moves from the hot feed stream to the cold  
24 permeate stream. The temperature gradient causes a difference in temperatures between the  
25 liquid–vapor interfaces and the bulk temperatures on both sides of the membrane. This effect is  
26 termed temperature polarization, and its magnitude is measured by the temperature polarization  
27 coefficient ( $\tau$ ), given by [9]:

$$28 \quad \tau = \frac{T_i - T_b}{T_h - T_c} \quad (1)$$

29 where,  $\tau$ , the temperature polarization coefficient, is used to represent the loss of thermal driving

1 force due to the thermal boundary layer resistances [2]. The value of  $\tau$  can approach unity for  
2 DCMD systems that have good fluid dynamic regimes.

3 There has been much MD research effort to understand how membrane properties affect the  
4 overall mass transfer and heat transfer processes, and they have generally focused on the  
5 development of improved membrane materials [10]. However, few articles have reported on the  
6 process design. In our previous work, the effect of operating parameters and membrane types  
7 were studied for an AGMD system [11, 12, 13] and also for a DCMD system in long term fouling  
8 trials [14]. In this work, the main objective is to investigate the effect of module dimensions on  
9 membrane flux.

10 To investigate the difference between co-current and counter-current flow modes and the effect  
11 of feed velocity, temperature and module geometry on flux and mass transfer coefficient, we used  
12 a commercially available hydrophobic, porous PTFE membrane for DCMD. The temperature  
13 distribution along the length of the module for both co-current and counter-current flow modes  
14 were measured and modeled, examining the relationship between flux and vapor pressure  
15 difference for both flow modes. To investigate the effect of linear velocity on permeation flux for  
16 both wide and short, and long and narrow module designs, the mass transfer coefficients for each  
17 condition were calculated for comparison between the module designs. To study the effect of salt  
18 concentration on flux and vapor pressure difference, a two dimension (2D) model based on  
19 energy, mass, and momentum balances was built to describe the DCMD process and predict pure  
20 water flux production. The simulated results were validated by comparing the predicted results  
21 with experimental results.

## 22 23 **2. Theoretical model**

24 Three layers including the feed channel, the membrane layer, and the permeate channel were  
25 built as shown in Fig. 1. In modeling the DCMD process, three transport processes were  
26 considered – energy convection and conduction for all three layers, momentum transport for the  
27 feed and the permeate channel, and mass transport for the membrane layer. The model geometry  
28 consists of a feed inlet boundary (E-G), a feed outlet boundary (F-H), a permeate inlet boundary  
29 (B-D), a permeate outlet boundary (A-C), a membrane layer vapor inlet boundary (E-F), and a

1 membrane layer vapor outlet boundary (C-D). It's total length  $L = \text{distance of (A-B)} = 0.4 \text{ m}$  (x-  
 2 direction), channel depth = distance of (A-C) = distance of (E-G) =  $0.001 \text{ m}$  (z-direction), and  
 3 membrane thickness = distance of (C-E) =  $0.0001 \text{ m}$  (z-direction). For simulation with a  
 4 reasonable computational expense, the following simplifying assumptions for the transport  
 5 equations were made: (i) steady incompressible flow for both feed and permeate; (ii) the  
 6 maximum Reynolds number for the experimental conditions is 468 and the flow is laminar; (iii)  
 7 the momentum of the permeate flow through the membrane is ignored; (iv) negligible heat loss to  
 8 the ambient environment; (v) steady state convection and conduction model for energy balance;  
 9 (vi) the mass transfer equations assume the dusty gas model is appropriate; and (vii) the  
 10 concentration polarization of low concentration NaCl solution (1%) is ignored to simplify the  
 11 calculation procedure and save CPU time.

12

## 13 **2. 1. Model equations**

### 14 **Feed channel**

15 The following equations in terms of pressure ( $P_h$ ), velocity ( $u_h$ ), and temperature ( $T_h$ ) were  
 16 derived. The incompressible Navier-Stokes equations were used for momentum balance:

$$17 \quad \rho_h (u_h \cdot \nabla) u_h = \nabla \cdot [-P_h I + \eta (\nabla u_h + (\nabla u_h)^T)] \quad (2)$$

$$18 \quad \nabla \cdot u_h = 0 \quad (3)$$

19 and the convection and conduction equations for the energy balance:

$$20 \quad \rho_h C_{p_h} u_h \cdot \nabla T_h - \nabla \cdot (k_h \nabla T_h) = 0 \quad (4)$$

21 where,  $\rho_h$  is the liquid density,  $C_{p_h}$  is the specific heat capacity at constant pressure, and  $k_h$  is the  
 22 liquid thermal conductivity (w/m·K).

23

### 24 **Membrane**

25 For the membrane layer, the flux flow was described as follows:

$$26 \quad J = \frac{1}{L} \int_0^L C_{(x)} (P_{(T1_{(xx)})} - P_{(T2_{(xx)})}) \quad (5)$$

27 where,  $C$  is the mass transfer coefficient, and the gas dusty model is used in this study [15];  $P$  is  
 28 the vapour pressure of water at the membrane surface, which can be calculated by the Antoine  
 29 equation [16].

1 The convection and conduction equations for the energy balance were:

$$2 \quad \rho_m C_{p_m} u_m \cdot \nabla T_m - \nabla \cdot (k_m \nabla T_m) = 0 \quad (6)$$

3 where,  $\rho_m$  is the membrane density;  $C_{p_m}$  is the specific heat capacity of membrane; and  $k_m$  is the  
 4 membrane thermal conductivity,  $k_m = \varepsilon \cdot k_{m_g} + (1 - \varepsilon) \cdot k_{m_s}$ . Here,  $\varepsilon$  is the membrane porosity,  
 5  $k_{m_g}$  and  $k_{m_s}$  refer to the thermal conductivity coefficients of vapor within the membrane pore and t  
 6 he solid membrane, respectively.

## 8 Permeate channel

9 For the permeate channel, the momentum and energy transport models are similar to the  
 10 equations used in feed channel, and the following equations in terms of pressure ( $P_c$ ), velocity  
 11 ( $u_c$ ), and temperature ( $T_c$ ) were derived.

$$12 \quad \rho_c (u_c \cdot \nabla) u_c = \nabla \cdot [-P_c I + \eta (\nabla u_c + (\nabla u_c)^T)] \quad (7)$$

$$13 \quad \nabla \cdot u_c = 0 \quad (8)$$

$$14 \quad \rho_c C_{p_c} u_c \cdot \nabla T_c - \nabla \cdot (k_c \nabla T_c) = 0 \quad (9)$$

15 where,  $\rho_c$  is the liquid density;  $C_{p_c}$  is the specific heat capacity; and  $k_c$  is the liquid thermal  
 16 conductivity, respectively.

## 18 2. 2. Model boundary conditions and solving the model

19 The following boundary conditions in dimensionless form were used.

20 For energy transfer via convection and conduction: the feed inlet boundary (E-G):  $T = T_{hi}$ ; The  
 21 permeate inlet boundary (B-D):  $T = T_{ci}$ ; The feed outlet boundary (F-H) and permeate outlet  
 22 boundary (A-C) were considered as convective flux:  $\mathbf{n} \cdot (-k \nabla T) = 0$ ; the membrane boundary  
 23 (E-F) and (C-D) were considered to be continuity heat flow:  $\mathbf{n} \cdot (q_1 - q_2) = 0$ ,  $q_i = -k_i \nabla T_i$ , ( $i$   
 24 = 1, 2); other boundary (A-B), (C-E), (D-F) and (G-H) were considered as thermal insulation: -  
 25  $\mathbf{n} \cdot (-k \nabla T) = 0$ .

26 For momentum equations: the feed inlet boundary (E-G):  $\mathbf{u} = u_h \cdot \mathbf{n}$ ; The permeate inlet  
 27 boundary (B-D):  $\mathbf{u} = -u_c \cdot \mathbf{n}$ ; The feed outlet boundary (F-H) and permeate outlet boundary (A-C)  
 28 were considered as no viscous stress:  $\eta (\nabla \mathbf{u} + (\nabla \mathbf{u})^T) \mathbf{n} = 0$ ,  $p = 0$ ; the other boundary (A-B),

1 (C-D), (E-F), (C-E), (D-F) and (G-H) were considered as wall:  $u = 0$ .

2 The fluxes were calculated using the sums of the local water flux, which depends on the vapor  
3 pressure difference and, therefore, the temperature difference across the membrane. To obtain the  
4 temperature distribution, the heat and mass transfer process of the DCMD module, all the  
5 equations above must be solved simultaneously. Defined all the constants and the expressions,  
6 mesh consists of 89360 elements, the Comsol multiphysics software was used to numerically  
7 solve the equations, using the boundary and initial conditions to calculate the distribution where  
8 the heat, velocity in the feed and permeate channels and flux flow through the membrane.

### 10 **3. Experimental**

#### 11 **3.1 Membrane module**

12 A flat-sheet module of 0.5 m length and 0.25 m width was fabricated. The membrane cell  
13 consisted of two compartments, the feed side and the permeate side. The compartments were  
14 made of High Density Polyethylene (HDPE) to resist corrosion by NaCl solutions and seawater.  
15 The cell was designed such that the water flows occurred either along the short (Y-Flow) or long  
16 (X-Flow) axis's, and Fig. 1 shows the difference between the X-Flow and Y-Flow modes. The X-  
17 Flow length was 0.4 m, and Y-Flow length was 0.15 m. The flow entered and left the MD module  
18 via flow distribution channels to ensure an even flow across the membrane.

19 This module design allowed the flow direction to be altered without the need to remove the  
20 membrane, and it thus reduced experimental errors associated with performance differences  
21 between membrane samples and handling of the membrane.

#### 23 **3.2 DCMD set up**

24 The DCMD experimental setup is schematically depicted in Fig. 2. The module was positioned  
25 horizontally so that the feed solution flowed through the bottom compartment of the cell while  
26 the cooling water passed through the upper compartment. The feed and the permeate were  
27 separated by a hydrophobic porous membrane, and the effective area of the membrane was 0.06  
28 m<sup>2</sup>. The feed and cold solutions were contained in double walled reservoirs and circulated  
29 through the membrane module using centrifugal pumps. The outlet temperatures of the hot and

1 cold sides were continually monitored and recorded electronically. The permeated liquid was  
2 circulated through a graduated cylinder, and the volume measured at regular intervals. The purity  
3 of the water extracted was determined through water conductivity using an electrical conductivity  
4 meter (EC470-L, ISTEK, KOREA).

5 A series of experiments were conducted on the DCMD system to investigate the effect of flow  
6 rates, flow configurations (counter-current vs. co-current), module dimensions (X-Flow vs. Y-  
7 Flow), salt concentration and temperature.

### 9 **3.3 Membrane and membrane characteristic method**

10 A commercially available hydrophobic porous PTFE membrane manufactured by GE  
11 Osmonics (Minnesota, USA) was used for the experiments. Some of the membrane  
12 characteristics provided by the manufacturer are listed in Table 1.

#### 14 **Liquid entry pressure (LEP) test**

15 For the measurement of the LEP, the membrane was placed in a filtration cell with an effective  
16 area of  $0.00039 \text{ m}^2$ , and the upper portion was filled with 20% NaCl solution. The filtration cell  
17 was placed in a beaker filled with pure water (Milli Q), such that the lower side of the filtration  
18 cell was in contact with the pure water. Pressure was applied to the 20% NaCl solution using  
19 regulated nitrogen. The pressure was increased until the NaCl solution penetrated through the  
20 membrane and was mixed with the pure water in the beaker. The penetration of the NaCl through  
21 the membrane was detected via a change in conductivity in the pure water by using a  
22 conductivity meter. The pressure at which the NaCl solution penetrated the membrane was  
23 recorded, and the average of three measurements for each of the three different samples of  
24 membrane was recorded [17].

#### 26 **Contact angle (CA) test**

27 The CA of the membrane was measured using a SV Sigma 701 Tensiometer from KSV  
28 Instruments Ltd (Helsinki, Finland). The membrane was brought into contact with a drop of pure  
29 water, and the CA was calculated with the aid of the computer software. The quoted CA is the

1 average of the three values of CA measurements.

2

### 3 Scanning electron microscopy (SEM) analysis

4 The morphology of the resulting membranes was examined by scanning electron microscopy  
5 (FE-SEM, Hitachi S-4800).

6

### 7 Gas permeability test

8 A gas permeability test was performed to verify the average pore size of the membrane. The  
9 test measured the flux at various pressure drops across the membrane using a single gas  
10 (nitrogen). Assuming the flow through the membrane is to be described by the Knudsen diffusion  
11 - Poiseuille flow mechanism, the total mass flux can then be obtained from:

$$12 \quad N = \left( \frac{8 \varepsilon r}{3 \xi \delta} \sqrt{\frac{1}{2 \pi R M T}} + \frac{\varepsilon r^3}{\xi \delta} \frac{1}{8 \eta} \frac{P_m}{R T} \right) \Delta P \quad (10)$$

13 where,  $\varepsilon$  is the porosity,  $r$  is the membrane pore radius,  $\xi$  is the membrane tortuosity,  $\delta$  is the  
14 membrane thickness,  $R$  is the gas constant,  $M$  is the molecular weight of the gas,  $T$  is the absolute  
15 temperature,  $\eta$  is viscosity,  $P_m$  is the average pressure within the membrane pores, and  $\Delta P$  is the  
16 pressure difference across the membrane.

17 The experimental was done at a constant pressure difference across the membrane ( $\Delta P = 1$  kPa).

18 Therefore, the equation has the form:

$$19 \quad N = A_0 + B_0 \cdot P_m$$

20 (11)

21 where  $A_0$  and  $B_0$  are constants [18].

22 From Eqs. (10) and (11), the membrane pore radius  $r$  and the effective porosity  $\varepsilon/\tau \cdot \delta$  can be  
23 obtained from  $A_0$  and  $B_0$  by the equation:

$$24 \quad r = \frac{16 B_0}{3 A_0} \sqrt{\frac{8 R T}{\pi M}} \eta \quad (12)$$

25 and,

$$26 \quad \frac{\varepsilon}{\xi \delta} = \frac{8 \eta R T B_0}{r^3} \quad (13)$$

27

## 1 **Capillary flow porometer test**

2 The pore size distribution of the membrane was determined using a Capillary Flow Porometer  
3 (Porous Materials, Inc., model CFP-1200-AE), which gives information about pore diameters in  
4 the 0.033 – 500  $\mu\text{m}$  range. The analysis was based upon a three-curve graph: dry curve, wet curve  
5 and half-dry curve. The membrane was immersed overnight in a low surface tension solution of  
6 porewick (16.0 dynes/cm) to ensure that the pores were fully saturated with the liquid. The  
7 wetting liquid, porewick, was displaced by compressed nitrogen, and the pore size was  
8 determined on the basis of the mean flow pressure when the half-dry curve intersected with the  
9 wet curve.

## 10 11 **4. Results**

### 12 **4.1 Membrane characteristics**

13 The membrane characteristic results are reported in Table 2. The CA of the membrane was  
14  $122 \pm 5^\circ$  and the LEP was  $160.1 \pm 2.5$  kPa. Both the CA and LEP results demonstrate the highly  
15 hydrophobic nature of the membrane.

16 Flux  $N$  versus pressure within the pores,  $P_m$ , was plotted from the gas permeability test results.  
17 Values for  $A_0$  and  $B_0$  were obtained from the intercept and slope of the straight line ( $A_0$  is the  
18 intercept from equation 11 and  $B_0$  is the slope), and values of  $3.08 \times 10^{-4}$  and  $1.04 \times 10^{-9}$  were  
19 obtained as per the method of [18]. The average pore diameter,  $2 \cdot r$ , was calculated from this  
20 technique using Eq. (12), and the effective porosity,  $\varepsilon/\tau \cdot \delta$ , was calculated to be  $17000 \text{ m}^{-1}$  from  
21 Eq. (13). The experiment was conducted three times, and the average membrane pore size was  
22  $0.28 \pm 0.05 \mu\text{m}$ .

23 Fig. 3 shows the pore size distribution for the membrane from the capillary flow porometer  
24 tests. The membrane exhibits a very narrow pore size distribution, with a mean pore size of  $0.27$   
25  $\mu\text{m}$ . The maximum pore diameter obtained from the bubble point data was  $0.39 \mu\text{m}$ . This result  
26 suggests that the sharp pore size distribution may minimize the potential water leakage through  
27 the membrane. The pore size results obtained from the gas permeability and the capillary flow  
28 porometer tests show an agreement similar to the  $0.22 \mu\text{m}$  value supplied by the manufacturer.

29 SEM images of the membrane surface are shown in Fig. 4 where the microstructures of the

1 membrane surface can be easily observed.

#### 3 **4.2 Effect of velocity on permeation flux and mass transfer coefficient**

4 Fig. 5 shows the effect of feed velocity on the flux for both the experimental results and  
5 modeling results under different feed inlet temperature conditions (NaCl concentration of 1%,  
6 counter-current, and X-Flow mode). The fluxes exhibit higher values when operated at higher  
7 temperature and higher velocity. It is widely understood that a temperature difference across an  
8 MD membrane will induce water vapor to pass and some amount of permeate is expected to be  
9 generated [19]. The flux increased with an increase in velocity from 0.17 m/s to 0.55 m/s, and it  
10 seems to reach the maximum values asymptotically for high velocity. This is attributed to the  
11 reduction of the boundary layer thickness when the Reynolds number increases, approaching a  
12 limiting value at velocities greater than 0.50 m/s [20]. The modeling results were compared with  
13 the experimental results from different velocity conditions. For lower temperature conditions,  
14 modeling results show a complete agreement with the experimental results. For the higher  
15 temperature curve, there was 8.6% difference between the model and experimental results when  
16 the velocity was 0.50 m/s. Table 3 lists the experimental and model results for hot side and cold  
17 side outlet temperatures. The modeling results show a good agreement with the experiment  
18 results, with errors of less than 5.0%. The two dimension model for DCMD based on the  
19 momentum, energy, and mass transfer is, therefore, accurate in its prediction of DCMD operation.

20 Fig. 6 (a) shows the effect of velocity on mass transfer coefficient for different temperature  
21 conditions for the counter-current flow mode. The mass transfer coefficient increased with an  
22 increase in velocity because of a reduction in temperature polarization as the flow rate and  
23 Reynolds number are increased and the boundary layer thickness is reduced [18]. The  
24 experimentally determined mass transfer coefficients were in the range of 0.0027 to 0.0042  
25  $L/m^2hrPa$ , and they were in the range of 0.0027 to 0.0038  $L/m^2hrPa$  for the model results. The  
26 values of mass transfer coefficient obtained in this study were similar to those reported by  
27 Termpiyakul [21]. The values of mass transfer coefficient plateau at high velocity, irrespective of  
28 the temperature, while the flux becomes constant for velocities greater than 0.50 m/s. Calculation  
29 of the mass transfer coefficient compensates for the changes in temperature gradient along the

1 membrane, while the flux incorporates this effect into its value. Therefore, the mass transfer  
2 coefficient is able to identify the fully developed conditions when the flow within the module is  
3 such that temperature polarization becomes constant (0.50 m/s), while the velocities continue to  
4 increase above this point because the temperature gradients along the membrane are lower and  
5 hence the temperature difference and vapour pressure differences remain high [22]. This is  
6 demonstrated by the temperature gradients along the membrane as shown in Fig. 6 (b). As the  
7 velocity increases, the temperature profiles flatten out until there is little temperature drop along  
8 the membrane (velocity higher than 0.50 m/s) and the driving force for membrane distillation  
9 remains constant with further increases in velocity.

#### 10 11 **4.3 Comparison of co-current and counter-current flow mode**

12 Fig. 7 shows the temperature distribution along the length of the module for co-current (a) and  
13 counter-current (b) flow modes detected by the thermometers under the conditions: NaCl  
14 concentration of 1%; hot side inlet temperature of 60°C, and cold side inlet temperature of 20°C,  
15 and both feed and permeate side linear velocity of 0.50 m/s for X-Flow mode. The temperature  
16 distribution profiles of permeate side and feed side are parallel to each other in counter-current  
17 flow mode, which is different from the curves of the co-current flow mode in which the curves  
18 approach each other [23]. The model simulated results were compared with the experimental  
19 results, and differences of less than 3.8% were obtained, which shows good agreement between  
20 the experimental and the modeling.

21 The values for vapor pressure difference for both co-current and counter-current flow modes  
22 are reported in Table 4. The temperatures were converted to vapor pressures using the Antoine  
23 Equation and the vapor pressure difference at each location calculated. The results indicate that  
24 there was a higher vapor pressure difference in the first half of the module (0.2 m) compared to  
25 the second half for the co-current mode. The vapor pressure difference for the counter current  
26 mode was even in each half. However, the average vapor pressure difference for the co-current  
27 and counter-current flow modes were similar.

28 Fig. 8 compares the experimental and modeling results for the effect of velocity on flux for  
29 both co-current and counter-current flow modes. The vapor pressure difference was calculated in

1 a manner similar to those shown in Table 4. At 40°C, the experimental results show good  
2 agreement with the modeling results for both the co-current and counter-current flow modes, and  
3 the fluxes for both modes were similar. However, at 60°C, the experimental results showed a  
4 higher flux for the co-current mode, while the modeling results predicted the counter-current  
5 mode to be a little higher. In the modeling case, the counter-current velocity is more efficient, as  
6 larger trans-membrane vapor pressure was created, and this prediction agreed with our small  
7 DCMD module experimental results mentioned in our previous work, and the Y-Flow mode  
8 results in section 4.4. The difference cannot be distinguished since the results are well within  
9 experimental error.

#### 11 **4.4 Comparison X-flow and Y-flow dimensions**

12 Fig. 9 (a) shows the effect of flow rate on the permeate flux for X-Flow and Y-Flow module  
13 arrangements for the following conditions: NaCl concentration of 1%; hot side inlet temperature  
14 of 60°C, and cold side inlet temperature of 20°C. The permeate flux increased with an increase in  
15 the flow rate from 1.5 L/min to 4.5 L/min, and it seemed to reach the maximum value for flow  
16 rates above 4.5 L/min in X-Flow mode for both co-current and counter-current flows. For the Y-  
17 Flow mode, the flux increased with an increase in the flow rate and did not reach a plateau for  
18 any experimental flow rate. As stated previously, the increasing of flux with flow rate is due to  
19 the reduction of the boundary layer thickness when the Reynolds number increases [17], as well  
20 as the reduction in temperature gradients along the membrane.

21 Before approaching the limiting value, the X-Flow mode shows a higher flux than Y-Flow.  
22 This is due to the X-Flow having a higher linear velocity under the same flow rate conditions,  
23 which reduces the boundary layer thickness and increases the temperature polarization coefficient,  
24  $\tau$ . This suggests that long, narrow modules are more appropriate for high flux modules than short,  
25 wide modules for a given flow rate.

26 Fig. 9 (b) shows the effect of velocity on flux for both co-current and counter-current flow  
27 modes for X-Flow and Y-Flow conditions. The Y-Flow mode showed a higher permeate flux for  
28 both co-current and counter-current flow modes under the same linear velocity conditions  
29 because the length or water path of the Y-Flow mode was shorter (0.15 m) than the X-Flow mode

1 (0.4 m), and, therefore, there was a lower temperature drop along the membrane for this  
2 configuration. In addition, the inside pressure of the module for different velocities was also  
3 observed, as shown in Fig. 9 (b). In the case of Y-Flow mode, the module's pressure increased  
4 rapidly with increasing velocity and reached 162 kPa at the velocity of 0.29 m/s. At the same  
5 time, the X-Flow mode showed a gradual increase of module pressure (105 kPa) at the velocity of  
6 0.56 m/s. In the case of Y-Flow, at 0.29 m/s the pressure in module had exceeded the tested  
7 membrane LEP value, i.e., 160 kPa, and salt solution penetrated some parts of the membrane  
8 instead of water vapor. This phenomenon resulted in an increase of the permeate conductivity  
9 from 22.6 to 64.5  $\mu\text{S}/\text{cm}$  within 3 hours. For the other conditions, the permeate conductivity  
10 decreased with time to less than 20  $\mu\text{S}/\text{cm}$  until steady state was reached, indicating that there  
11 was no salt passage across the membrane for these conditions. Furthermore, high pressure can  
12 lead directly to leakage problems, which would require more robust apparatus where leaks do not  
13 occur. Ultimately, the desalination process was not able to continue at higher velocities for the Y-  
14 Flow mode.

15 As the Y-Flow mode was able to produce a higher flux at a given velocity, Fig. 9 (a) showed  
16 that the X-Flow mode flux was higher for a given flow rate. Therefore, under the conditions of  
17 limited membrane area and flow rate, the X-Flow mode (long skinny module) is the most  
18 productive because of the reduced temperature polarization effects. The Y-Flow mode (short,  
19 wide module) has the advantage of having a larger temperature difference, and hence the vapor  
20 pressure difference across the membrane at any given feed velocity. However, at velocities for  
21 which temperature polarization effects are reduced (i.e., above velocities for which the mass  
22 transfer coefficient becomes constant), the temperature gradients along the membrane were  
23 reduced and the vapor pressure differences for the X-Flow and Y-Flow modes approach each  
24 other. Additionally, the long membrane length in the X-Flow mode had lower hot brine outlet  
25 temperatures, and hence more thermal energy was utilized in this geometry.

26

#### 27 **4.5 Effect of NaCl concentration on permeation flux**

28 Table 5 shows the effect of salt concentration on the flux and vapor pressure difference in the  
29 counter-current X-Flow mode for the conditions of a hot side temperature of 60°C, a cold side

1 temperature of 20°C and velocity of 0.50 m/s. The permeation flux decreased approximately  
2 10.9% from 24.2 to 21.5 L/m<sup>2</sup>hr when the NaCl concentration increased from 1 to 6 wt %. The  
3 vapor pressure difference decreased by approximately 4.8% from 5.83 kPa to 5.55 kPa when the  
4 NaCl concentration increased from 1 to 6 wt %. The effect of salt concentration on the flux shows  
5 a decrease stronger than the vapor pressure difference. The reason may be attributed to the  
6 membrane surface temperature polarization, which was ignored when calculating the vapor  
7 pressure difference. The polarization layers formed on either side of PTFE membrane reduce  
8 water permeation in membrane distillation. This reduction is higher when the concentration  
9 increases. This is the result of two opposing contributions: first, the heat transfer coefficient  
10 decreased slightly with higher salt concentration, i.e., at higher salt concentration, the solution  
11 viscosity becomes higher. Ultimately the thermal conductivity becomes lower, and it reduces the  
12 convective heat transfer. Secondly the slower heat transfer kinetics from the bulk flow to the  
13 membrane surface increases the temperature polarization.

14

## 15 **5. Conclusions**

16 DCMD experiments were performed using a PTFE membrane with a mean pore size of 0.28  
17 μm and an effective porosity value of 17000 m<sup>-1</sup>. The results of the CA and LEP tests indicate  
18 that the membrane is suitable for DCMD because of its high hydrophobicity.

19 The fluxes exhibit higher values when operated at higher temperature and higher velocity, and  
20 they seem to reach maximum values asymptotically at high velocity. The values of mass transfer  
21 coefficients observed in this study were in the range of 0.0027 to 0.0042 L/m<sup>2</sup>hrPa.

22 The temperature distribution profiles of permeate side and feed side were parallel to each other  
23 in the counter-current flow mode, while the temperature profiles approach each other in the co-  
24 current flow. The flux and vapor pressure differences obtained for co-current and counter-current  
25 values were less than 5.0%, in other words, equal to each other.

26 The permeation flux increased with an increase in the flow rate and velocity, reaching  
27 maximum values asymptotically in the X-Flow mode, but there was no plateau for the Y-Flow  
28 mode over the flow rate range considered in these experiments. The Y-Flow mode has the  
29 advantage of having wider temperature difference at given feed velocity, but the X-Flow mode

1 had lower inside pressure and lower hot brine outlet temperatures, which means that more  
2 thermal energy was utilized.

3 Both the flux and vapor pressure differences decreased with an increase in the NaCl  
4 concentration. The effect of salt concentration on flux showed a decrease greater than the vapor  
5 pressure difference, and was attributed to polarization layers formed on the membrane.

6 A two dimension model was developed through the membrane by integrating the permeate flux  
7 with mass, energy and momentum balances on both feed and permeate sides. The modeling  
8 results agreed well with the experimental results for different velocity and temperature conditions,  
9 and both the experimental and simulation results were in accord with each other.

10

### 11 **Acknowledgment**

12 This research was conducted as part of the project by the Ministry of Commerce, Industry and  
13 Energy (MOCIE) through Regional Innovation Centre (RIC). The research was partially  
14 supported by a grant (07 SEAHERO B01-04-02) from the Plant Technology Advancement  
15 Program funded by the Ministry of Construction & Transportation of the Korean government.

16

### 17 **Nomenclature**

18  $A_0$  constant

19  $B_0$  constant

20  $C$  mass transfer coefficient

21  $C_{pc}$  cold side specific heat capacity at constant pressure

22  $C_{ph}$  hot side specific heat capacity at constant pressure

23  $C_{pm}$  specific heat capacity of the membrane at constant pressure

24  $I$  matrix I

25  $i$  x-direction any position i

26  $J$  permeate flux

27  $k$  thermal conductivity (w/m·K)

28  $k_c$  cold side liquid thermal conductivity (w/m·K)

1	$k_h$	hot side liquid thermal conductivity (w/m·K)
2	$k_m$	liquid thermal conductivity of the membrane (w/m·K)
3	$k_{mg}$	liquid thermal conductivity of the membrane (w/m·K)
4	$k_{ms}$	liquid thermal conductivity of the membrane (w/m·K)
5	$L$	module length
6	$M$	molecular weight of water
7	$N$	gas flux
8	$n$	matrix n
9	$P$	pressure
10	$P_1$	saturated vapor pressure on the hot side membrane surface (Pa)
11	$P_2$	saturated vapor pressure on the cold membrane surface (Pa)
12	$P_c$	cold side pressure (Pa)
13	$P_h$	hot side pressure (Pa)
14	$q$	inward heat flux (w/m <sup>2</sup> )
15	$r$	membrane pore radius
16	$R$	gas constant
17	$T_1$	hot side membrane surface temperature (°C)
18	$T_2$	cold side membrane surface temperature (°C)
19	$T_c$	cold side temperature (°C)
20	$T_{c,i}$	cold side inlet temperature (°C)
21	$T_{c,o}$	cold side outlet temperature (°C)
22	$T_h$	hot side temperature (°C)
23	$T_{h,i}$	hot side inlet temperature (°C)
24	$T_{h,o}$	hot side outlet temperature (°C)
25	$T_m$	membrane temperature (°C)
26	$u_c$	cold side flow velocity (m/s)
27	$u_h$	hot side flow velocity (m/s)
28	$u_m$	flow velocity inside of membrane layer (m/s)
29	$v_{c,i}$	cold side inlet flow velocity (x-direction)

1  $v_{h,i}$  hot side inlet flow velocity (x-direction)  
2  $x$  x-direction  
3  $z$  z-direction  
4

5 *Greek letters*

6  $\tau$  temperature polarization coefficient  
7  $\rho_c$  cold side liquid density  
8  $\rho_h$  hot side liquid density  
9  $\rho_m$  membrane density  
10  $\varepsilon$  membrane porosity  
11  $\zeta$  membrane tortuosity  
12  $\delta$  membrane thickness  
13  $\eta$  viscosity  
14

15 **References**

- 16 [1] L. Carlsson, The new generation in sea water desalination SU membrane distillation system,  
17 Desalination 45 (1983) 221-222.
- 18 [2] R. W. Schofield, A. G. Fane, C. J. D. Fell, Heat and mass transfer in membrane distillation,  
19 J. Membr. Sci. 33 (1987) 299-313.
- 20 [3] A. M. Alklaibi, N. Lior, Membrane-distillation desalination: Status and potential,  
21 Desalination 171 (2005) 111-131.
- 22 [4] S. Bandini, C. Gostoli, G. C. Sarti, Separation efficiency in vacuum membrane distillation,  
23 J. Membr. Sci. 73 (1992) 217-229.
- 24 [5] L. Basini, G. D. Angelo, M. Gobbi, G.C. Sarti, C. Gostoli, A desalination process through  
25 sweeping gas membrane distillation, Desalination 64 (1987) 245-257.
- 26 [6] M. C. García-Payo, M. A. Izquierdo-Gil, C. Fernández-Pineda, Air gap membrane  
27 distillation of aqueous alcohol solutions, J. Membr. Sci. 169 (2000) 61-80.
- 28 [7] M. Tomaszewska, Membrane distillation-examples of applications in technology and  
29 environmental protection, Environmental Studies 9 (2000) 27.

- 1 [8] G. C. Sarti, C. Gostoli, S. Bandini, Extraction of organic components from aqueous streams  
2 by vacuum membrane distillation, *J. Membr. Sci.* 80 (1993) 21-33.
- 3 [9] W. T. Hanbury, T. Hodgkiess, Membrane distillation - an assessment, *Desalination* 56  
4 (1985) 287-297.
- 5 [10] S. I. Andersson, N. Kjellander, B. Rodesjö, Design and field tests of a new membrane  
6 distillation desalination process, *Desalination* 56 (1985) 345-354.
- 7 [11] R. Thiruvenkatachari, M. Manickam, T. O. Kwona, S. J. Kim, I. S. Moon, Separation of  
8 water and nitric acid with porous hydrophobic membrane by air gap membrane distillation,  
9 *Separ. Sci. Technol.* 41 (2006) 3187-3199.
- 10 [12] M. Manickam, T. O. Kwon, J. W. Kim, M. Duke, S. Gray, I. S. Moon, Effects of operating  
11 parameters on permeation flux for desalination of sodium chloride solution using air gap  
12 membrane distillation, *Desalination and Water Treatment* 13 (2010) 362-368.
- 13 [13] K. He, H. J. Hwang, I. S. Moon, Air gap membrane distillation (AGMD) on the different  
14 types of membrane, *Korean J. Chem. Eng.* accepted, (2010).
- 15 [14] K. He, H. J. Hwang, M. W. Woo, I. S. Moon, Production of Drinking Water from Saline  
16 Water by Direct Contact Membrane Distillation (DCMD), *J. Ind. Eng. Chem.* in press, 16  
17 (2010).
- 18 [15] R. W. Schofield, A. G. Fane, C. J. D. Fell, Gas and vapor transport through micro-porous  
19 membranes. I. Knudsen-Poiseuille transition, *J. Membr. Sci.* 53 (1990) 279-294.
- 20 [16] R. M. Felder, R. W. Rousseau, *Elementary Principles of Chemical Processes*, third ed., John  
21 Wiley & Sons, New York, 2000.
- 22 [17] J. Zhang, N. Dow, M. Duke, E. Ostarcevic, J. D. Li, S. Gray, Identification of material and  
23 physical features of membrane distillation membranes for high performance desalination, *J.*  
24 *Membr. Sci.* 349 (2010) 295-303.
- 25 [18] M. S. El-Bourawi, Z. Ding, R. Ma, M. Khayet, A framework for better understanding  
26 membrane distillation separation process, *J. Membr. Sci.* 285 (2006) 4-29.
- 27 [19] E. Curcio, E. Drioli, *Membrane Distillation and Related Operation – A Review*, *Sep. Purif.*  
28 *Rev.* 34 (2005) 35 – 86.

- 1 [20] K. W. Lawson, D. R. Lloyd, Membrane distillation, *J. Membr. Sci.* 124 (1997) 1-2.
- 2 [21] P. Termpiyakul, R. Jiratananon, S. Srisurichan, Heat and mass transfer characteristics of a  
3 direct contact membrane distillation process for desalination, *Desalination* 177 (2005) 133-  
4 141.
- 5 [22] J. Phattaranawik, R. Jiratananon, Direct contact membrane distillation: effect of mass  
6 transfer on heat transfer, *J. Membr. Sci.* 188 (2001) 137-143.
- 7 [23] L. Martinez-Diez, F. J. Florido-Diaz, Distillation of brines by membrane distillation,  
8 *Desalination* 137 (2001) 267-273.


9

10

## Figure captions

- 1
- 2 Fig. 1. Schematic diagram of the simulated DCMD 2D model. (Counter-current)
- 3 **Fig. 2.** Membrane modules for X-Flow and Y-Flow modes.
- 4 **Fig. 3.** Schematic diagram of DCMD experimental setup.
- 5 **Fig. 4.** Pore size distribution of the PTFE membrane.
- 6 **Fig. 5.** SEM images of the membrane surface (a) and a higher magnified view (b).
- 7 **Fig. 6.** Experimental (Exp.) results and simulation (Mod.) results showing the effect of velocity
- 8 on permeate flux for different temperature conditions. (Cold side inlet temperature of
- 9 20°C, NaCl concentration of 1%, counter-current and X-Flow mode)
- 10 **Fig. 7.** Effect of velocity on mass transfer coefficient (a) and vapor pressure difference (b). (Cold
- 11 side inlet temperature of 20°C, NaCl concentration of 1%, counter-current and X-Flow
- 12 mode)
- 13 **Fig. 8.** Measured and predicted temperature distribution along the membrane for co-current (a)
- 14 and counter-current (b) flow modes. (Hot and cold side velocity of 0.50 m/s, NaCl
- 15 concentration of 1%, and X-Flow mode)
- 16 **Fig. 9.** Comparison of experimental and modeling results for co-current and counter-current flow
- 17 modes on permeate flux for different velocity conditions. (Cold side temperature of 20°C,
- 18 NaCl concentration of 1%, and X-Flow mode)
- 19 **Fig. 10.** Comparison different flow modes on permeate flux: (a) Effect of flow rate on permeate
- 20 flux; (b) Effect of linear velocity on flux and module inside pressure (Pre.). (NaCl
- 21 concentration of 1%; hot side inlet temperature of 60°C, and cold side inlet temperature of
- 22 20°C)
- 23
- 24
- 25
- 26
- 27
- 28
- 29


1  
2  
3  
4

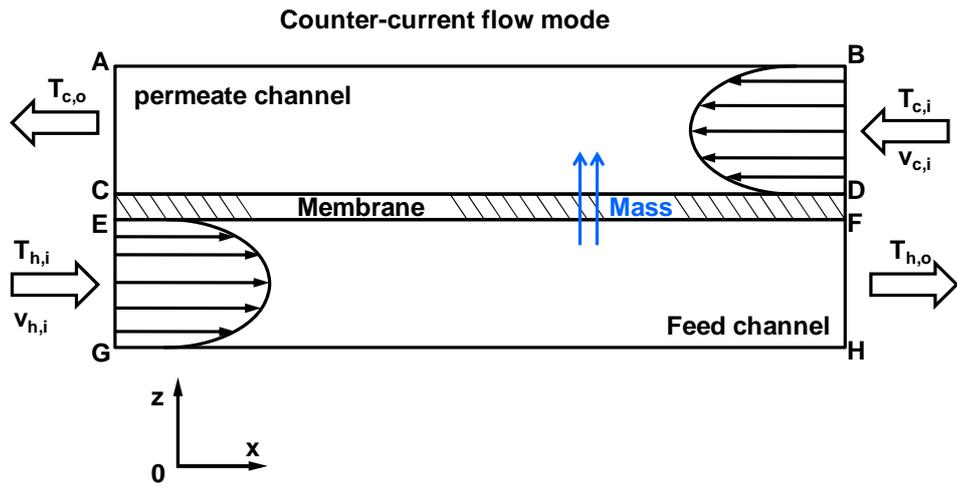

5  
6  
7  
8  
9  
10  
11

Fig. 1.


1  
2  
3

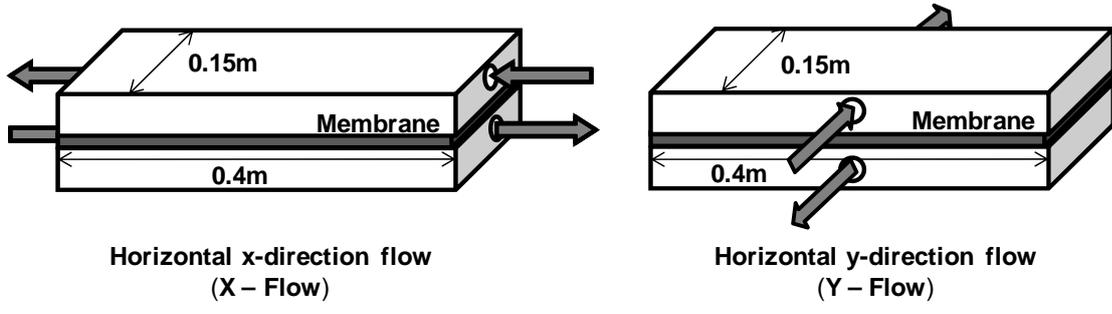

4  
5  
6  
7  
8

Fig. 2.

1  
2  
3  
4

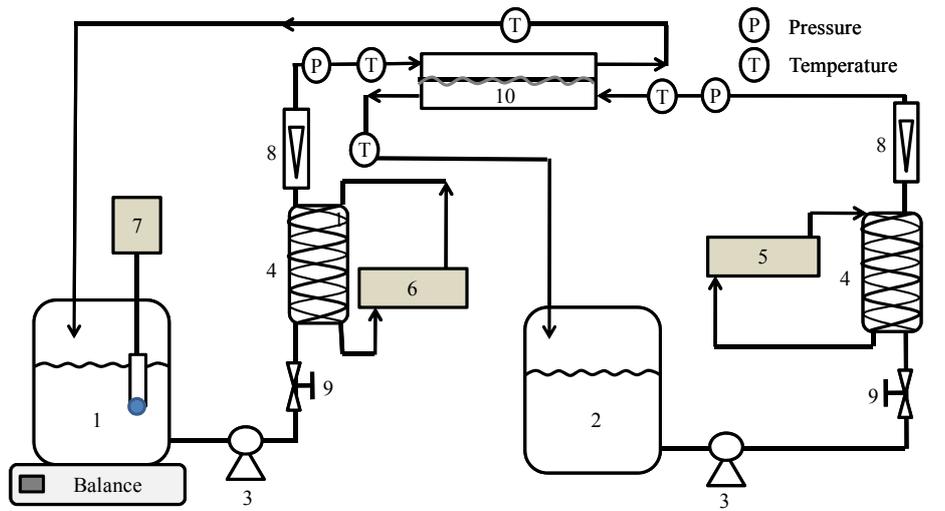

1. Permeate tank, 2. Feed tank, 3. Pump, 4. Heat Exchanger, 5. Heater, 6. Chiller, 7. Conductivity meter, 8. Flow meter, 9. Flow controller, 10. Membrane

5  
6  
7  
8  
9

**Fig. 3.**

1  
2  
3  
4  
5  
6


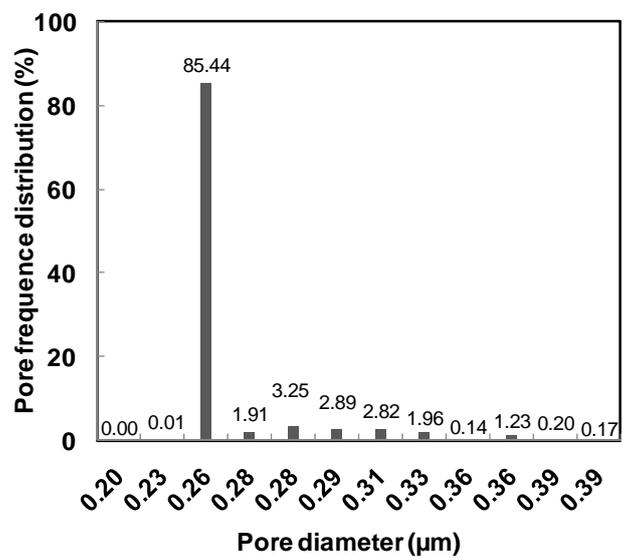


Fig. 4.

7  
8  
9

1  
2  
3  
4  
5  
6  
7

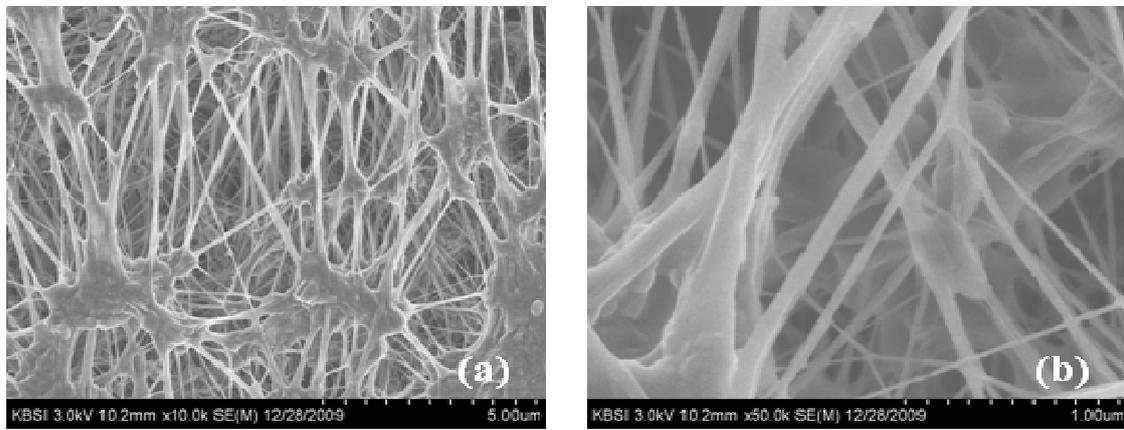

8  
9  
10

**Fig. 5.**

1  
2  
3  
4  
5  
6



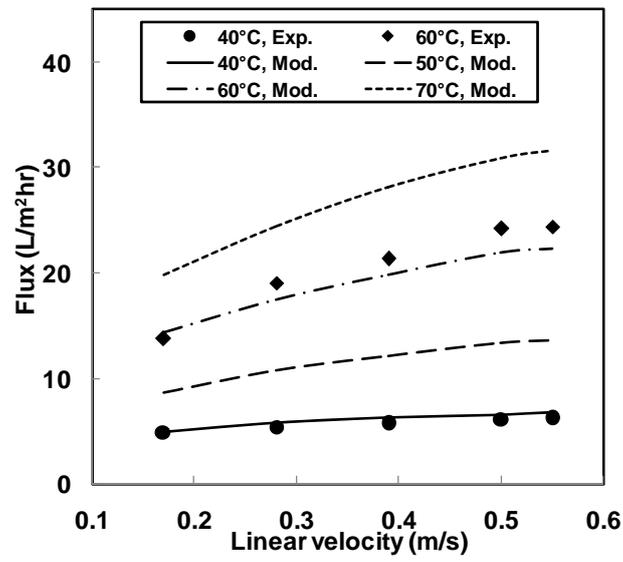


Fig. 6.

7  
8  
9  
10

1  
2  
3  
4

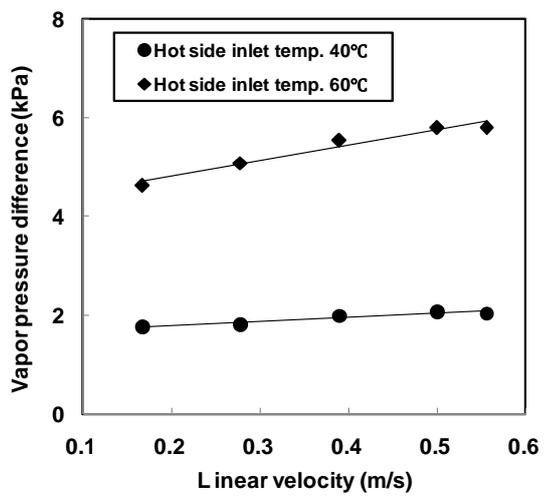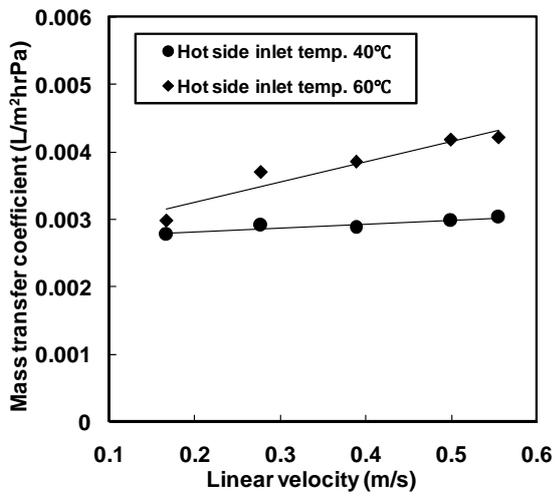

5  
6  
7  
8  
9  
10

(a)


(b)

Fig. 7.

1

2

3

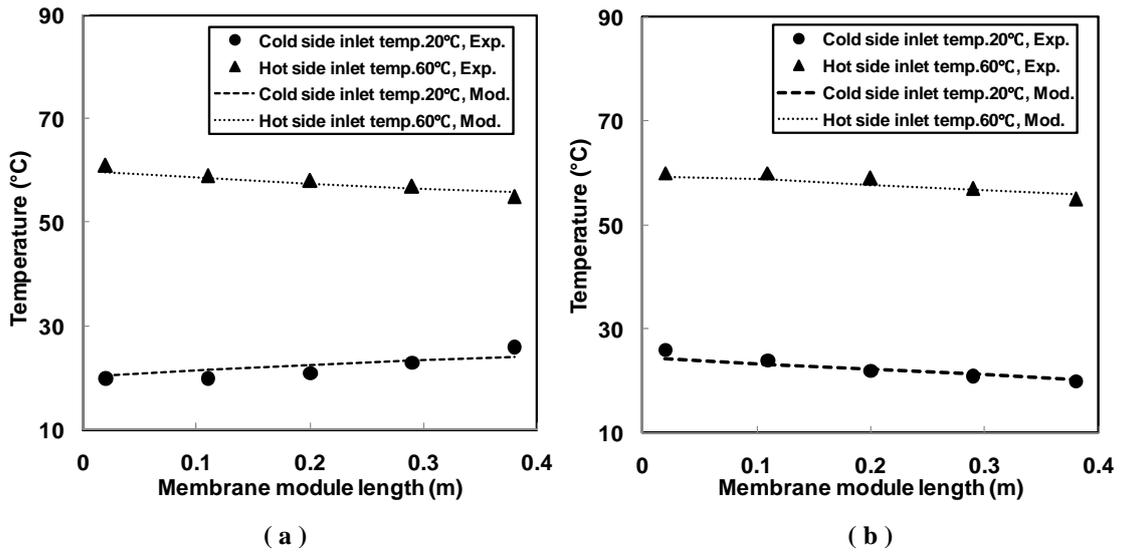

4

5

6

7

Fig. 8.

1  
2  
3  
4  
5


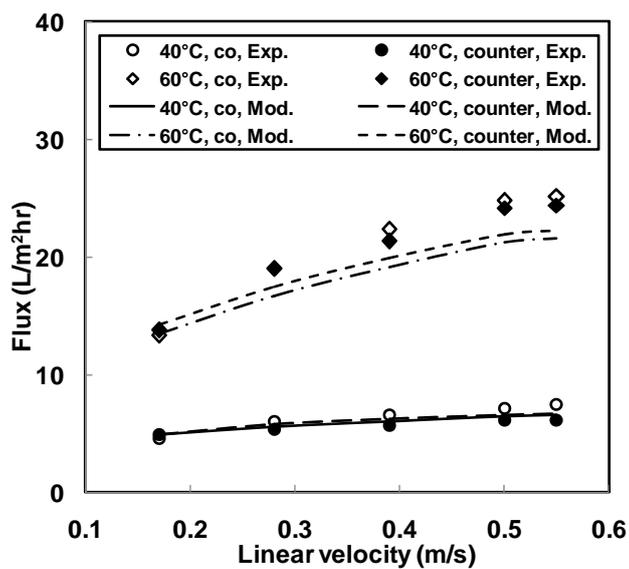



Fig. 9.

6  
7  
8

1  
2  
3  
4  
5  
6

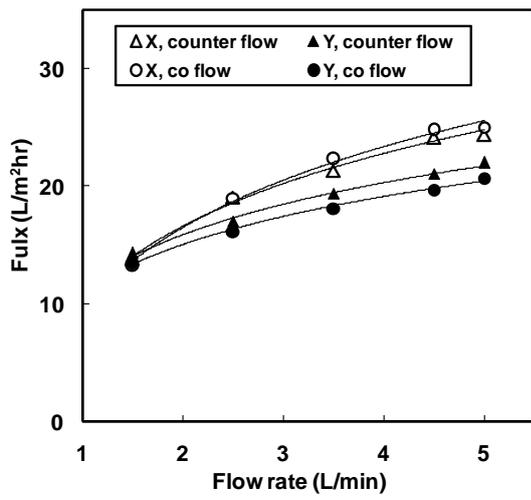

(a)

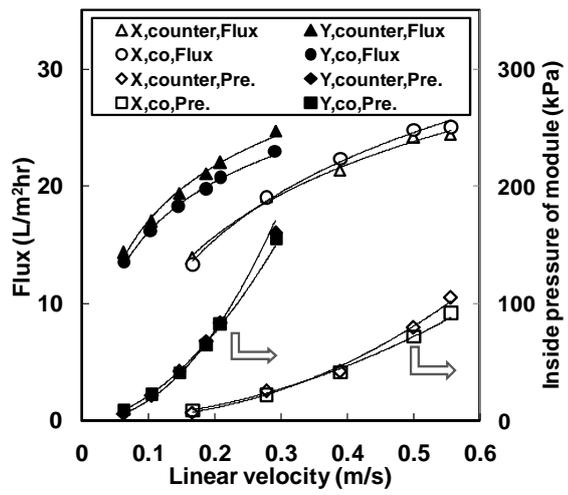

(b)

Fig. 10.

7  
8  
9  
10  
11  
12

1 **Tables**

2 **Table 1** Membrane characteristics provide by manufacture.

3 **Table 2** Membrane characteristics from various tests.

4 **Table 3** Comparison the temperature profile for both experiment result and modeling results. (Hot  
5 side inlet temperature of 60°C, cold side inlet temperature of 20°C, NaCl concentration 1%,  
6 counter-current, X-Flow mode)

7 **Table 4** Comparison of vapor pressure difference for co-current and counter-current flow mode.  
8 (Hot side inlet temperature of 60°C, cold side inlet temperature of 20°C, Hot side velocity of 0.5  
9 m/s, cold side velocity of 0.5 m/s, NaCl concentration of 1%, and X-Flow mode)

10 **Table 5** The effect of NaCl concentration on flux and vapor pressure difference. (Hot side inlet  
11 temperature of 60°C, and cold side inlet temperature of 20°C; hot side velocity of 0.5  
12 m/s, cold side velocity of 0.5 m/s; counter-current, X-Flow mode)

13

14

15

16

17

1

**Table 1**

Membrane	Properties
Membrane material	PTFE (Polytetrafluoroethylene)
Support material	Scrim
Nominal pore size	0.22 $\mu\text{m}$
Total thickness	0.110 mm
Active layer porosity	83%

2

3

4

1

2

3

4

5

**Table 2**

Characteristics	Values
LEP	160.1±2.5 kPa
Contact angle	122 ±5°
Pore size from gas permeability test	0.28±0.05 μm
Pore size from capillary flow porometry test	0.27 μm
$\varepsilon/\tau \cdot \delta$ from gas permeability test	17000 m <sup>-1</sup>

6

1  
2  
3  
4  
5  
6  
7  
8

**Table 3**

Velocity (m/s)	Hot outlet temp. (°C)			Cold outlet temp. (°C)		
	Experimental	Modeling	Error (%)	Experimental	Modeling	Error (%)
0.17	50.1	49.5	1.20	29.1	30.5	2.81
0.28	52.3	52.7	0.76	27.4	27.4	0.36
0.39	53.9	54.3	0.74	26.3	25.7	2.28
0.5	55.1	55.3	0.36	25.8	24.7	4.26
0.55	55.3	55.7	0.72	25.4	24.5	3.54

9  
10  
11

1  
2  
3  
4  
5

**Table 4**

Module length (m)	$\Delta V_{p,counter}$ (kPa)	$\Delta V_{p,co}$ (kPa)
0.02	5.602	7.662
0.11	5.921	6.874
0.20	6.256	6.256
0.29	5.921	5.198
0.38	5.602	3.656
Average	5.861	5.909

6  
7  
8

1

2

3

4

5

**Table 5**

Feed concentration (%)	Flux (L/m <sup>2</sup> hr)	Vapor pressure difference (kPa)
1	24.18	5.83
3.5	22.89	5.76
6	21.54	5.55

6

7